arXiv:cond-mat/0006479v2 [cond-mat.supr-con] 20 Jul 2000

Discrimination between the superconducting gap and the pseudo-gap in Bi2212 from intrinsic tunneling spectroscopy in magnetic field

V.M.Krasnov[1,2], A.E.Kovalev[2], A.Yurgens[1,3] and D.Winkler[1,4]
[1] Department of Microelectronics and Nanoscience, Chalmers University of Technology, S-41296 Göteborg, Sweden
[2] Institute of Solid State Physics, 142432 Chernogolovka, Russia
[3] P.L.Kapitza Institute, 117334 Moscow, Russia
[4] IMEGO Institute, Aschebergsgatan 46, S41133, Göteborg, Sweden

(February 1, 2008)

Intrinsic tunneling spectroscopy in high magnetic field (H) is used for a direct test of superconducting features in a quasiparticle density of states of high-T_c superconductors. We were able to distinguish with a great clarity two co-existing gaps: (i) the superconducting gap, which closes as $H \rightarrow H_{c2}(T)$ and $T \rightarrow T_c(H)$, and (ii) the c-axis pseudo-gap, which does not change neither with H, nor T. Strikingly different magnetic field dependencies, together with previously observed different temperature dependencies of the two gaps [1], speak against the superconducting origin of the pseudo-gap.

PACS numbers: 74.25.-q, 74.50.+r, 74.72.Hs, 74.80.Dm

A pseudo-gap (PG) in the electronic density of states (DOS) of high-T_c superconductors (HTSC) has been established by different experimental techniques [1–10], at temperatures well above the superconducting critical temperature T_c. Surface tunneling measurements [2,4] indicated that the superconducting gap (SG) is almost temperature (T) independent, merging into the pseudo-gap at $T \approx T_c$; the latter can exist up to room temperature. In contrast to ordinary superconductors, the gap in DOS of HTSC was reported to be uncorrelation to T_c and increased with underdoping despite a decrease in T_c [11]. This has lead to a suggestion that electron pairs are preformed at high temperature but do not condense into a coherent state until at T_c [12]. Surface tunneling, however, has drawbacks in its sensitivity to surface deterioration [13]. At present there is no consensus about the origin of the PG, the correlation between SG and PG, or the dependencies of both gaps on material and experimental parameters. A clarification of these issues is certainly important for understanding HTSC.

The most crucial test for the superconducting origin of the two gaps is their magnetic field (H) dependencies. Magnetic field is a strong depairing factor and destroys superconductivity when the field exceeds the upper critical field H_{c2}. So far the magnetic field dependence of the pseudo-gap in HTSC is highly controversial. For example, in YBaCuO compounds the NMR spin-lattice relaxation rate above T_c, which reflects the spin part of the PG, was reported to decrease [7], increase [8], or to be independent of magnetic field [9,10]. Surface tunneling measurements in Bi2212 revealed the existence of the PG inside the vortex core [14]. However, the authors argued that it is due to the precursor superconductivity mechanism, similar, as they believe, to what happens at $T > T_c$. Clearly, the magnetic field dependence of the pseudo-gap is far from being established and advanced measurements with alternative technique are necessary.

Intrinsic tunneling spectroscopy is a powerful method to study the quasiparticle DOS inside bulk HTSC single crystals [1,15,16]. This method allows avoiding the problem of surface deterioration. On the other hand, it has several problems too, such as stacking faults (defects) in the sample, injection of non-equilibrium excitations or internal heating [17]. Using small area mesa structures, it is possible to avoid mixing between out-of-plane (c-axis) and in-plane transport. Moreover, a probability of having stacking faults in the mesa decreases, as well as the overheating. Thus clean and clear c-axis tunneling characteristics can be obtained and used for studying DOS [1].

In this paper we study magnetic field dependencies of the superconducting gap and the pseudo-gap in small $Bi_2Sr_2CaCu_2O_{8+x}$ (Bi2212) mesas. The intrinsic tunneling characteristics exhibit two distinct features: a sharp superconducting peak and a smooth dip-and-hump feature, attributed to the c-axis pseudo-gap in the tunneling DOS. We have observed that the SG and the PG not only may have different magnitudes, but also have strikingly different dependencies both versus H and T: the SG closes as $H \rightarrow H_{c2}$ and $T \rightarrow T_c$; while the PG does not change neither with H, nor T and persists in the superconducting state. This unambiguously indicates the coexistence of the two gaps and rules out the precursor superconductivity scenario of the PG.

Small mesa structures, of area down to 2 μm^2 were made on top of Bi2212 single crystals by photolithography, Ar-ion etching and a self-alignment technique [1]. Such mesas represent stacks of intrinsic Josephson junction, formed by the crystalline structure of HTSC [18] and exhibit behavior typical for stacks of SIS (Superconductor-Insulator-Superconductor) type Josephson junctions. For example, Fiske steps and Fraunhofer oscillations were observed in Ref. [19] and multiple Josephson fluxon modes were observed in

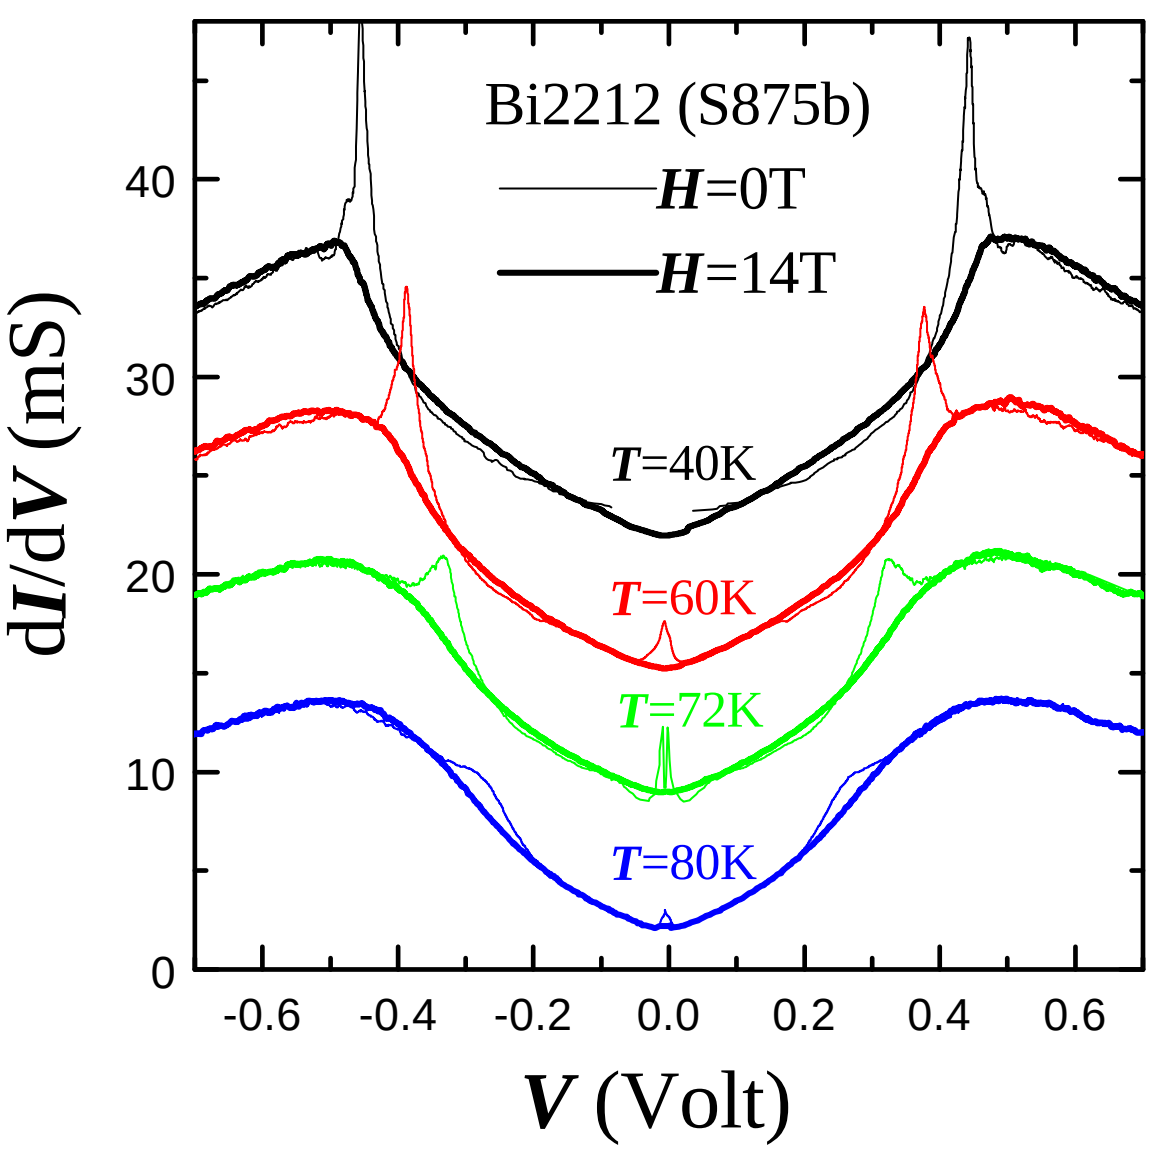

FIG. 1. Differential conductance curves for a pure Bi2212 mesa at different temperatures for H =0 (thin lines) and H = 14T (thick lines). The existence of a (T, H) dependent superconducting peak and the (T, H) independent "background" pseudo-gap dip-and-hump is clearly seen

Ref. [20]. Here we present results for pure Bi2212 and intercalated HgBr$_2$-Bi2212 samples. The Bi2212 samples are near optimally doped ($T_c \simeq$ 92 K). The intercalated samples are overdoped, as follows from a small PG and more metallic temperature dependence of the c-axis resistance. Upon intercalation with HgBr$_2$ molecules, the distance between cuprate layers increases and the c-axis resistivity increases while the critical current density decreases by a factor of 10-20 as compared to the pristine sample [21]. This leads to a decrease of both dissipated power and overheating during measurements. T_c is decreased by intercalation to ∼73 K. The c-axis IVC's were measured in a three probe configuration. The differential conductance, $\sigma = dI/dV$, was measured by lock-in technique with the AC current of 10μA.

In Fig. 1, c-axis $\sigma = dI/dV$ vs. V, curves are shown for a pure Bi2212 mesa ($5 \times 6.5 \mu m^2$, N = 7 intrinsic Josephson junctions) at four different temperatures, $T < T_c$. Curves are displayed both for H=0 (thin lines) and H=14T (thick lines) along the c-axis. For clarity, the curves for different T are shifted sequentially by 7 mS along the vertical axis.

The $\sigma(V)$ curves have a temperature independent resistance at large bias [1], as expected for pure tunnel junctions. At low T and H there is a sharp superconducting peak at the sum-gap voltage, $V_s = 2N\Delta_S/e$, where N is the number of junctions in the mesa and Δ_s is the superconducting gap [22]. For SIS junctions, the superconducting peak should disappear simultaneously with superconductivity both as $T \to T_c$ and $H \to H_{c2}$ [23]. Indeed, from Fig. 1 it is seen that with increasing T, the peak shifts to smaller voltages, reduces in amplitude and eventually disappears as T_c is approached [1]. It is also seen that the superconducting peak is very sensitive to magnetic field and vanishes at large fields.

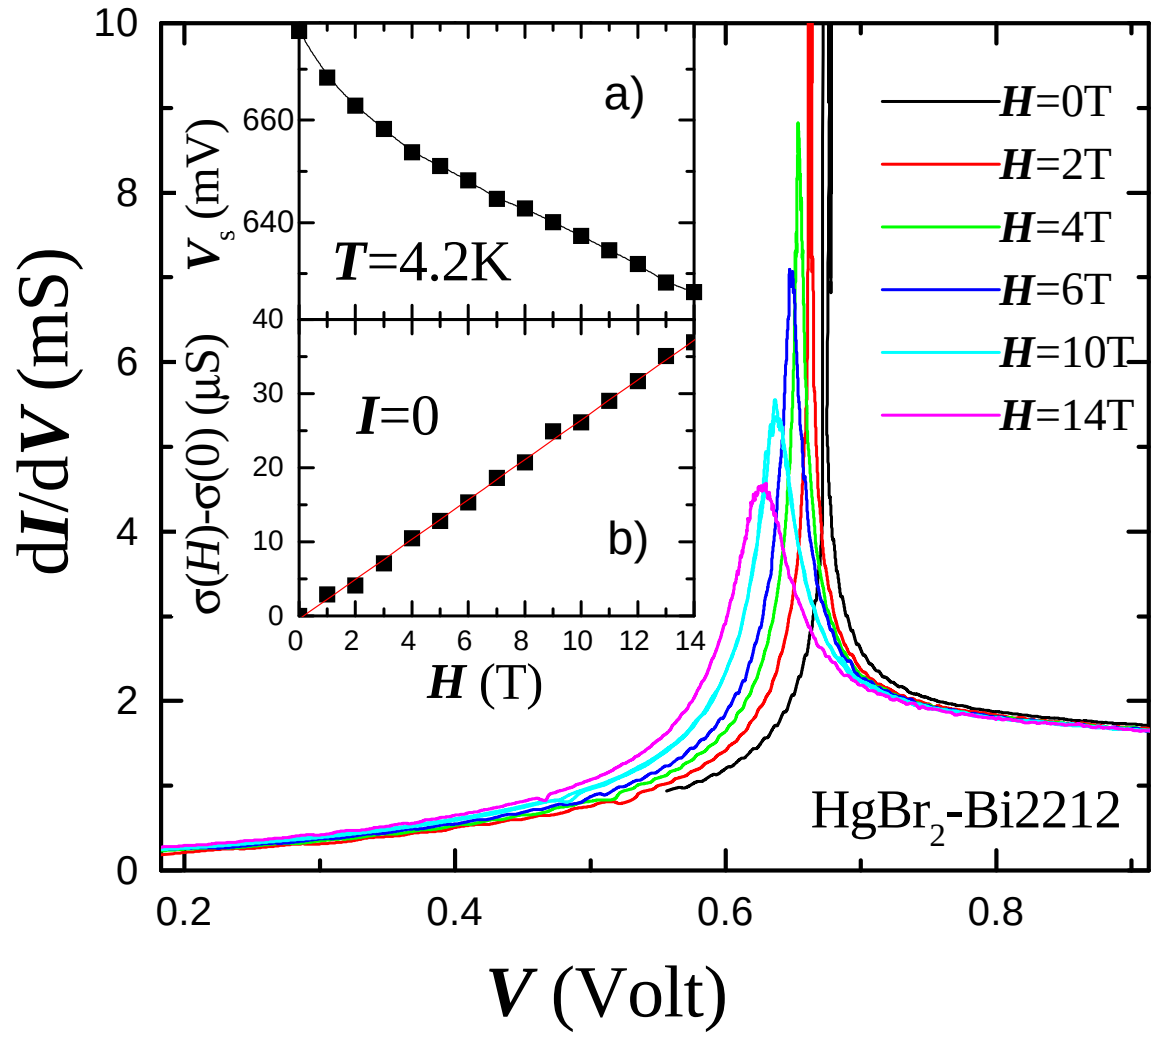

FIG. 2. Differential conductance of the intercalated mesa at T =4.2K, for different $H \parallel c$. Insets show a) the decrease of the peak voltage, V_s, and b) the linear increase of a zero-bias conductance with H.

In Fig. 2, $\sigma(V)$ curves of the intercalated HgBr$_2$-Bi2212 mesa are shown for different $H \parallel c$ at low temperature T=4.2K. It is seen that the superconducting peak reduces in amplitude with increasing field and systematically shifts to a lower voltage, as shown in inset a). Likewise, the zero bias conductance, $\sigma(I = 0)$, increases linearly with H, showing negative magnetoresistance, see inset b). Such behavior is typical for SIS junctions at low temperature in perpendicular magnetic fields both for s-wave [23] and d-wave superconductors with uncorrelated vortices [24]. Here, the decrease of V_s reflects the decrease of the maximal Δ_s and the linear increase of $\sigma(I = 0)$ is associated with a linear increase of the vortex density.

In Fig. 3, $\sigma(V)$ curves of the same pure Bi2212 mesa as in Fig. 1. are shown for high temperatures, a) $T \simeq$72K and b) $T \simeq$80K, and for several $H \parallel c$. Unlike the case of low T, for $T >$ 70K the superconducting peak is completely suppressed at H =14 T. With increasing H, the $\sigma(V)$ curves approach some magnetic field independent "background" curve, e.g., from Fig. 3 b) it is clearly seen that there are no changes in the $\sigma(V)$ curves for $H >$10T. Taking the field at which the superconducting peak disappears and the magnetoresistance at $V \sim V_s$ saturates as the upper critical field, we estimate $H_{c2}(\parallel c) \simeq$ 10T at T =80 K and $\simeq$ 14T at T =72K, in agreement with previously obtained values, see, e.g., Ref. [24].

However, despite vanishing of the superconducting peak, the IVC's remain nonlinear at $H > H_{c2}(T)$. The background $\sigma(V)$ curves exhibit a smooth depletion of the zero-bias conductance (a dip) plus a hump at a certain voltage $V = V_{pg}$, see Fig. 1. The background curve

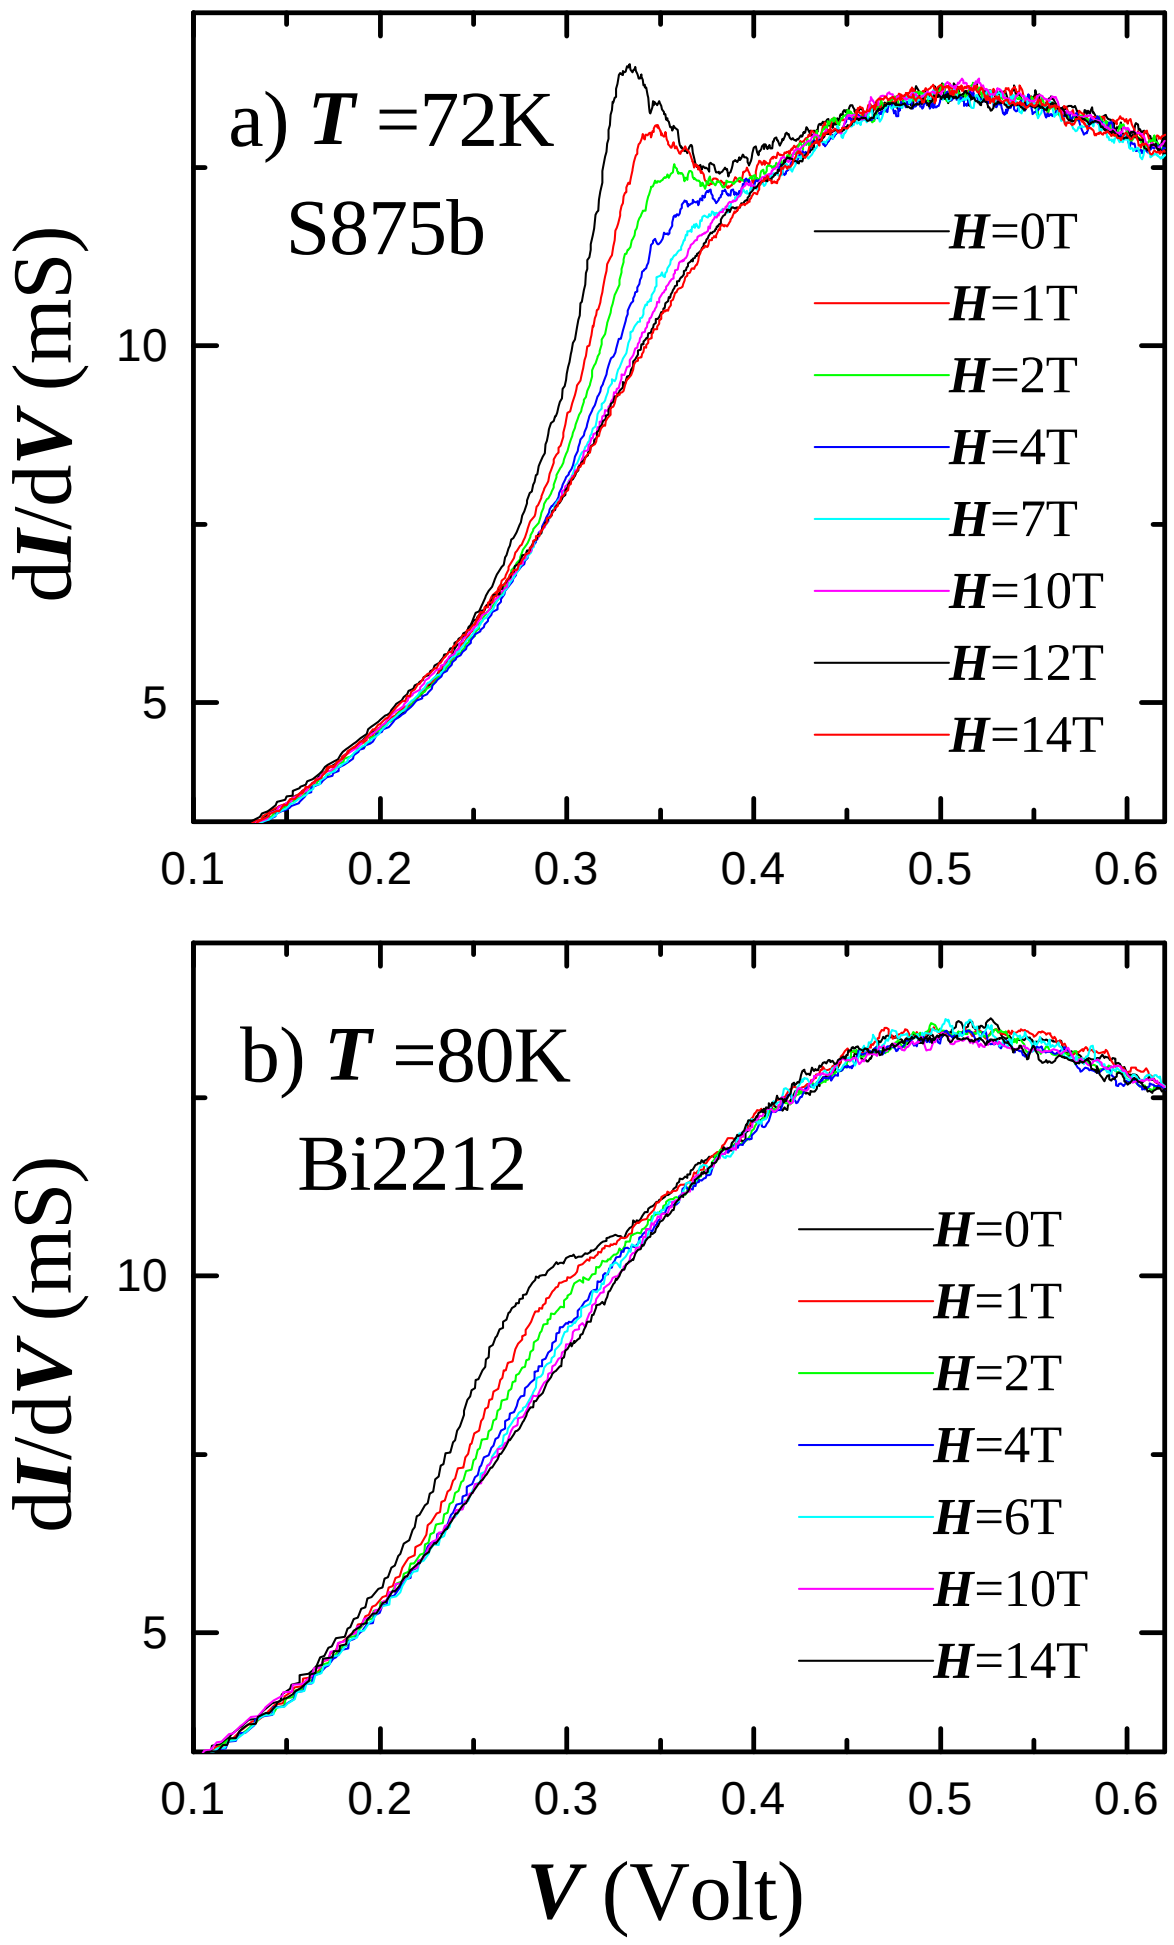

FIG. 3. $\sigma(V)$ curves of a pure Bi2212 mesa at a) T =72K and b) $T = 80$ K and for several $H \parallel c$. It is seen that the superconducting peak is completely suppressed in high fields, while the "background" PG dip-and-hump structure remains magnetic field independent. It is clear that the superconducting peak and the PG hump appear at different voltages.

is similar to that observed in the vortex core [14] and, to our opinion, represents the bare normal (non-superconducting) state with the remaining PG in the tunneling DOS even at $T < T_c$. Fig. 1 demonstrates that the PG hump voltage V_{pg} is almost independent of T [1] and is completely independent of H within the applied field range. The latter is most clearly demonstrated in Fig. 3 b), from which it is seen that there are no changes neither of the shape nor of the position of the PG hump with H. Moreover, it is seen that the PG hump voltage, V_{pg}, is distinctly different from the superconducting peak voltage, V_s. The striking contrast in magnetic field dependencies of the superconducting gap and the pseudogap is the central observation of this paper.

At high T, the behavior of $\sigma(V)$ becomes more complicated: First, the superconducting peak does not move to lower voltages with increasing H and second, the subgap conductance, $\sigma(0)$, becomes almost independent of H. To some extent such anomalous behavior may be due to the fact that at high T and H, the $\sigma(V)$ of a SIS junction does not follow the quasi-particle DOS [22]. As a matter of fact, for $T/T_c \gtrsim 0.5$ the peak in $\sigma(V)$ can shift to a higher voltage, as a result of a strong smearing, despite the decrease of Δ_s [23]. In addition, the peak in the spatially averaged DOS itself smears and shifts towards higher energies with H, see, e.g., Fig. 18 from Ref. [25]. Similarly, the $\sigma(0)$ can even decrease with H despite the increase of DOS($E = 0$) [23]. However, numerical simulations showed that the subgap conductance of a SIS junction should still have some H-dependence, which is obviously not the case for $V < 0.25$V in Fig.3 a).

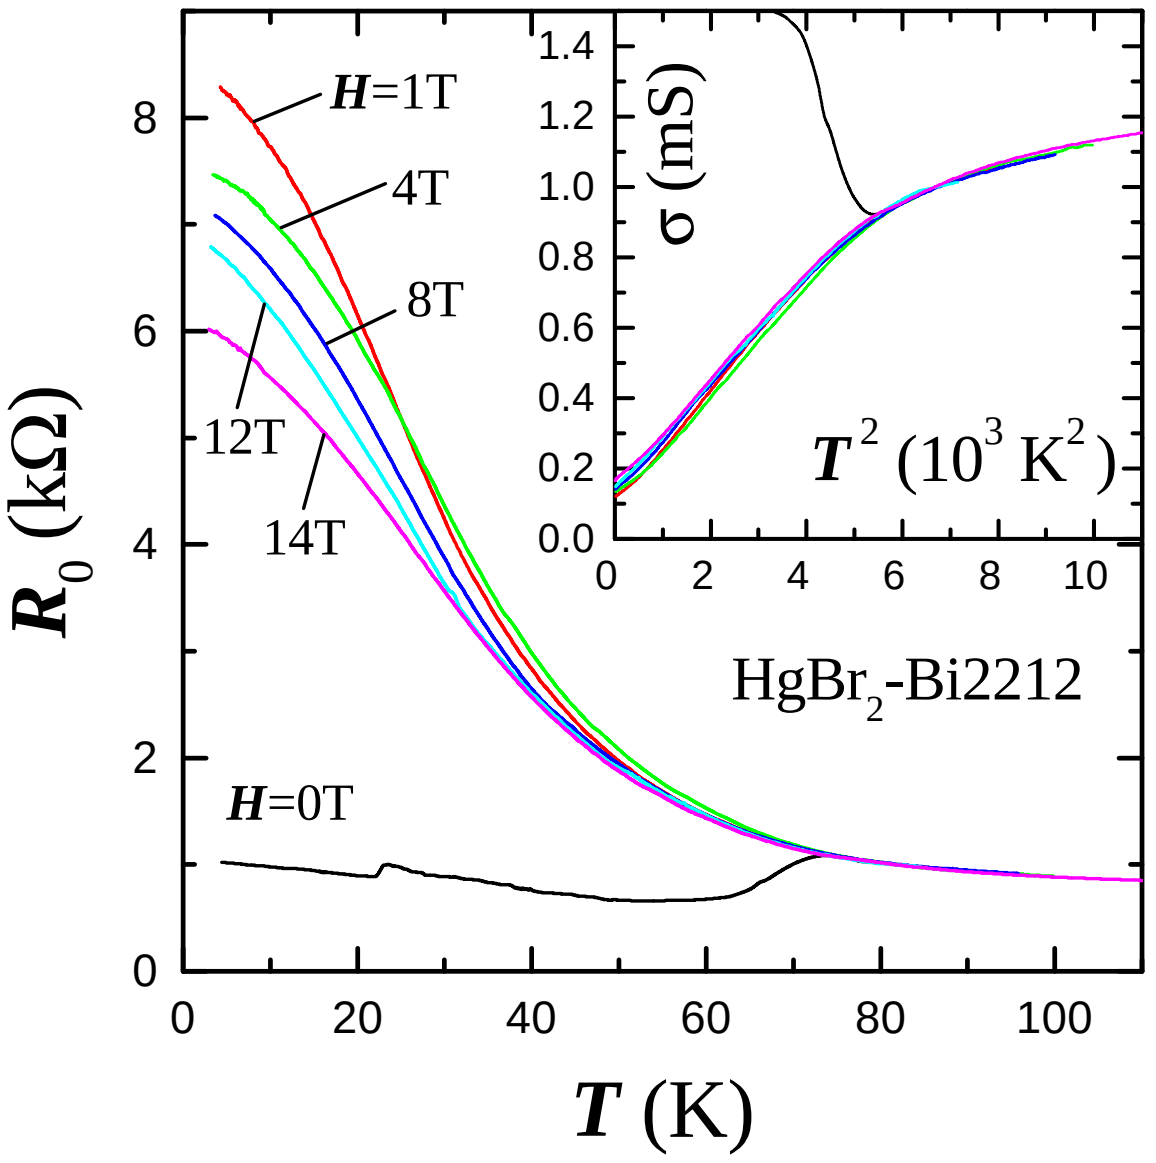

FIG. 4. Temperature dependence of the zero-bias resistance of the intercalated mesa at several $H \parallel c$. It is seen that R_0 decreases with increasing H and approaches a universal magnetic field independent "background" curve. Inset demonstrates the T^2 dependence of the zero-bias conductance at low temperatures.

We believe that the observed discrepancy between numerical simulations and experimental data at high T and H, is due to the PG, persisting at $T < T_c$. Indeed, the phenomenon appears at high T, when the T-dependent SG becomes considerably less than the T-independent PG. Furthermore, the anomalous behaviour is more pronounced for the near optimally doped Bi2212 with a larger PG, than for overdoped HgBr$_2$-Bi2212 samples with a smaller PG. If so, the suppression of subgap conductance at $T > 60$K, for the pure Bi2212 mesa, see Fig. 1, is mostly due to the PG rather than to the SG.

Fig. 4, shows temperature dependencies of the zero-bias resistance R_0 of the intercalated sample at several H. The intercalated sample is remarkable in the respect, that the critical current can be completely suppressed by a small H. Thus it was possible to trace the quasiparticle resistance in the whole range of T and H. At low T, the R_0 continuously decreases ($\sigma(0)$ increases) with field, as shown in inset b) of Fig. 2. The range of variation of $R_0(H)$ decreases with increasing T. At high H and T, e.g. in Fig.4 for H >12 T and T >35 K, the $R_0(T)$ curves collapse into a single semiconducting curve. This "background", magnetic field independent resistance represents the persisting PG, rather than the SG, as discussed above. The inset in Fig. 4 shows the zero-bias conductance vs. T- square for the same data. It is seen that $\sigma(0) \propto T^2$, at low T. In Ref. [24] such a behavior was attributed to a d-wave character of the superconducting state. However, we should emphasize that in our case the zero-bias conductance is not entirely determined by the SG, but a significant part of it originates from the magnetic field independent "background" PG conductance. The inset in Fig. 4 shows that the background conductance at H =14T and T >30K is still reasonably well described by the T^2 dependence. This may indicate that the PG also has a d-wave symmetry [2]. The behavior of $R_0(T, H)$ of pure, near optimally doped Bi2212 mesas is similar [26], but quantitatively different. First of all the PG in those samples is significantly larger than in overdoped intercalated HgBr$_2$-Bi2212 samples, in agreement with a general trend, known from previous studies [1–6]. Therefore, the magnetic field independent "background" PG resistance is a larger fraction of R_0 and the magnetoresistance at zero bias decreases considerably, as can be seen from Figs. 1 and 3. We should also note, that for optimally doped mesas $\sigma(0)$ deviates from the T^2 dependence and shows a tendency to vanish at $T \rightarrow 0$.

In conclusion, we have performed intrinsic tunneling spectroscopy of small HTSC mesa structures in high magnetic fields. Such measurements yield a crucial test for the high-T_c superconductivity, since a high magnetic field is a strong depairing factor. The intrinsic tunneling conductance curves exhibit two distinct features: (i) the sharp peak at low temperatures and (ii) the smooth dip-and-hump structure at high temperatures. As we have shown, the two features can be clearly separated due to their strikingly different magnetic field dependencies: the low-T peak vanishes both as $H \rightarrow H_{c2}(T)$ and $T \rightarrow T_c(H)$, while the dip-and-hump does not change with neither H, nor T. This allowed us to unambiguously attribute the peak to the superconducting gap and the dip-and-hump to the non-superconducting c-axis pseudo-gap in tunneling DOS. Our data indicate that the PG neither disappear, nor transform into the SG below T_c. Indeed, at intermediate T and H, the superconducting peak emerges on top of the PG dip-and-hump feature at a distinctly lower voltage, $V_s < V_{pg}$, see Fig. 3. Furthermore, at high H we were able to completely suppress the superconducting peak/gap and observed the bare pseudo-gap state clearly persisting at T well below $T_c(H = 0)$. In experiment, such state is characterized by saturation of the magnetoresistance and appearance of the "background", (T, H)-independent nonlinear conductance, see Figs. 3 and 4. The obtained results speak in favor of two different co-existing gaps in the tunneling DOS of HTSC. This casts serious doubts to the precursor superconductivity scenarios of the c-axis pseudo-gap and related HTSC theories, which require a similar origin and behaviour of the SG and the PG. We hope that our observation together with the growing experimental evidence for an independent behavior of SG and PG [1,3,5,6,9,10], will help consolidating efforts to understand the pseudo-gap phenomenon and the high-T_c superconductivity.

The work was supported by the Swedish Superconductivity Consortium and NFR. SnL (Göteborg) facilities were used for sample fabrication. Magnetic field measurements were performed at ISSP (Chernogolovka). We are grateful to V.V.Ryazanov for the support of this work, to A.A.Golubov for the assistance in numerical simulations, to J.-H. Choy for providing us with intercalated crystals, to T.Claeson and P.Delsing for critical reading the manuscript.

---

[1] V.M. Krasnov et al., *Phys.Rev.Lett.* **84**, 5860 (2000)

[2] A.G.Loeser et al., *Science* **273**, 325 (1996)

[3] A.V. Puchkov et al., *J. Phys. Cond. Mat.* **8**, 10049 (1996)

[4] Ch.Renner et al., *Phys. Rev. Lett.* **80**, 149 (1998)

[5] J.Demsar et al., *Phys. Rev. Lett.* **82**, 4918 (1999)

[6] J.L.Tallon and J.W.Loram, *Cond-Mat*/**0005063**

[7] P.Carreta et al., *Phys. Rev. B* **54**, R9682 (1996)

[8] V.F.Mitrovic et al., *Phys. Rev. Lett.* **82**, 2784 (1999)

[9] K. Gorny et al., *Phys. Rev. Lett.* **82**, 177 (1999)

[10] G-Q. Zheng et al., *Phys. Rev. B* **60**, R9947 (1999)

[11] N. Miyakawa et al., *Phys. Rev. Lett.* **80**, 157 (1998)

[12] M. Randeira, *Cond-Mat*/**9710223**

[13] T. Cren et al., *Cond-Mat*/**0006039**

[14] Ch.Renner et al., *Phys. Rev. Lett.* **80**, 3606 (1998)

[15] K. Schlenga et al., *Phys. Rev. B* **57**, 14518 (1998)

[16] M. Suzuki et al., *Phys. Rev. Lett.* **82**, 5361 (1999)

[17] P.J.Thomas et al., *Cond-mat*/**0001365**

[18] R. Kleiner and P. Müller, *Phys. Rev.* B **49**, 1327 (1994)

[19] V.M. Krasnov et al., *Phys.Rev.B* **59**, 8463 (1999)

[20] V.M. Krasnov et al., *Phys.Rev.B* **61**, 766 (2000)

[21] A. Yurgens et al., *Int. J. Mod. Phys.* B **13**, 3758 (1999); J.-H. Choy et al., *J. Am. Chem. Soc.* **119**, 1624 (1997)

[22] We measure spatially averaged characteristics. In the mixed state, Δ_s is spatially nonuniform due to a presence of Abricosov vortices. At low T the peak represents the maximal superconducting gap, $\Delta_s(max)$, between the vortices. However, at higher T the correlation between the peak position and $\Delta_s(max)$ is lost and V_s becomes systematically larger than $2\Delta_s(max)/e$.

[23] A.A.Golubov and M.Yu.Kupriyanov, *J. Low Temp.Phys.* **70**, 83 (1988)

[24] N.Morozov et al., *Phys.Rev.Lett.* **84**, 1784 (2000)

[25] M.Ichioka et al., *Phys.Rev.B* **59**, 8902 (1999)

[26] A.Yurgens et al., *Phys. Rev. B* **59**, 7196 (1999)